

EFFECT OF THE MQL TECHNIQUE ON CUTTING FORCE AND SURFACE QUALITY DURING THE SLOT MILLING OF TITANIUM ALLOY

VPLIV TEHNIKE MQL NA SILO REZANJA IN KVALITETO POVRŠINE MED REZKANJEM UTOROV NA TITANOVI ZLITINI

Khaled Ali Osman¹, Volkan Yilmaz^{2*}, Hakki Özgür Ünver³, Ulvi Şeker⁴,
S. Engin Kiliç⁵

¹Atılım University, 06836 Ankara, Turkey

²Gazi University, Ankara, 06500, Turkey

³TOBB University of Economics and Technology, 06520 Ankara Turkey,

⁴Gazi University, Besevler, Ankara, 06570, Turkey

⁵Atılım University, 06830, Ankara, Turkey

Prejem rokopisa – received: 2021-08-02; sprejem za objavo – accepted for publication: 2021-11-22

doi:10.17222/mit.2021.236

In this study, the effects of four control parameters, i.e., the cutting speed (v_c), feed per tooth (f), depth of cut (a_p), and flow rate of the cutting fluid (Q), on the surface roughness (R_a) and cutting force (F_c) were investigated in the slot milling of titanium alloys (Ti-6Al-4V). The effects of the control parameters were determined by a statistical analysis. In addition, RSM models for R_a and F_c during machining under three cooling/lubrication conditions, i.e., dry, flood, and minimum quantity lubrication (MQL), were obtained. The results revealed that both R_a and F_c are sensitive to changes in f , a_p and Q . It was found that the MQL condition generates lower values of R_a where the surface roughness value is $0.227 \mu\text{m}$. By contrast, F_c values under the MQL condition were close to those of the flood condition and at times even better. The machining performance at a cutting-fluid flow rate of 36 mL/h under the MQL condition was found to be the best under certain machining conditions. MQL was found to be an effective alternative technique for conventional conditions when machining Ti-6Al-4V.

Keywords: sustainable manufacturing, titanium, milling, minimum quantity lubrication

V tem članku avtorji opisujejo raziskavo vpliva štirih kontrolnih parametrov; to je: hitrosti rezanja (v_c), koraka podajanja na posamezni utor (f), globine reza (a_p) in pretoka maziva (Q) na hrapavost površine (R_a) in silo rezanja (F_c) med rezkanjem utorov na titanovi zlitini vrste Ti-6Al-4V. Vpliv kontrolnih parametrov so avtorji določili s pomočjo statistične analize. Na ta način so s pomočjo modelov RSM (angl.: Response Surface Methodology) dodatno dobili vrednosti za R_a in F_c med mehansko obdelavo pri treh različnih pogojih ohlajanja oziroma mazanja. Ti pogoji so bili: na suho oz. brez dodajanja maziva, intenzivno oz. močno (obdelovanec je potopljen v mazivo) in z minimalno količino maziva (angl.: minimum quantity lubrication (MQL)). Rezultati raziskav so pokazali, da sta R_a in F_c občutljiva na spremembe vseh kontrolnih parametrov f , a_p in Q . Avtorji ugotavljajo, da pri preizkusnih pogojih z MQL dobijo manjšo vrednost površinske hrapavosti ($R_a = 0.227 \mu\text{m}$). Medtem, ko so bile vrednosti za silo rezanja F_c pri MQL podobne tistim, ki so jih dobili pri intenzivnem mazanju oz. v nekaterih primerih celo manjše. Na osnovi izvedenih preizkusov in raziskav avtorji ugotavljajo, da so dosegli najboljše pogoje rezkanja utorov na izbrani Ti zlitini pri MQL oz. hitrosti pretoka maziva 36 mL/h . Ugotavljajo da je MQL učinkovita alternativna tehnika mazanja konvencionalnim pogojem mazanja med mehansko obdelavo zlitine tipa Ti-6Al-4V.

Ključne besede: trajnostna proizvodnja, titan, rezkanje, minimalna količina maziva (MQL)

1 INTRODUCTION

In the field of machining, there is a recent trend toward making machining processes eco-friendly. In this regard, numerous effective strategies have been proposed as alternatives to cutting fluids, including minimum quantity lubrication (MQL), a technique regarded as both economically and environmentally friendly.¹ During machining, large quantities of cutting fluids are supplied to the contact zone between the cutting tool and the workpiece to avoid thermal damage.² However, the cost of the cutting fluids relative to the overall manufacturing cost is high. In addition, cutting fluids can have unhealthy impacts on workers and the surrounding environ-

ment.^{3,4} Therefore, to counter these effects, many sustainable technologies have recently been developed to supply cutting fluids during the machining process using less or no cutting fluids. One of the interesting sustainable technologies is minimum quantity lubrication (MQL), which is considered economically and environmentally friendly.⁵⁻⁷ MQL consists of a mixture of pressurized air and oil micro droplets applied directly to the cutting zone.^{8,9} **Table 1** classifies the flow rates of the cutting fluids applied with the MQL technique.

According to the literature, the MQL technique appears to provide good results and is a promising alternative to conventional cooling and lubricating methods.¹⁵⁻¹⁷ In this context, many researchers have studied the effects of utilizing MQL under various machining processes. In line with these initiatives, Joshi et al.¹⁸ turned an Incoloy

*Corresponding author's e-mail:
volkan@gazi.edu.tr (Volkan Yilmaz)

Table 1: Different ranges for flow rate of air-fluid mixture reported in the literature

References	Flow-rate ranges
10	2–300 mL/h
11, 12	10–100 mL/h
13	50–500 mL/h
14	less than or equal to 1 mL/h

800 alloy using three different lubrication conditions: flood, dry and MQL. Their results revealed that the lowest surface roughness (R_a) and tool wear occurred when machining under MQL cooling conditions. Similar results achieved by^{19–21} revealed that under MQL conditions, all the values related to the cutting forces (F_c), surface roughness and tool tip temperature were significantly lower than those of the flood condition. J. Sun et al.²² conducted a milling process on a Ti-6Al-4V titanium alloy with carbide tools under MQL, dry, and flood coolant conditions. This study demonstrated that MQL could be effectively used as a coolant method in end-milling. New advances in cooling techniques along with developments in cutting-fluid types aim at improved machining productivity based on sustainability. Yet, they require predictive models for performance machining processes to create new techniques at low cost.²³ The predictive model helps to clarify the relationship be-

tween the quality response and the control parameters. It also includes optimal cutting conditions, coolant or lubricant types, and cutting tools.^{24–27} In **Table 2**, a summary of key studies are provided.

2 EXPERIMENTAL PART

2.1 Machine tool, workpiece material and cutting tool

All of the slot-milling experiments were carried out on a three-axis CNC milling machine (VMC 550 JOHNFORD) with a maximum spindle rotation of 8000 min⁻¹. Machining tests were conducted using coated cementite carbide (coated Al-Cr-Ni). The cutting-tool diameter is 10 mm with a flat-end mill and four teeth. In all experiments, the titanium alloy Ti-6Al-4V (grade 5) was used as the workpiece material, together with a nozzle setup, as shown schematically in **Figure 1**. Meanwhile, **Figure 2** shows the experimental setup. Before the experiment, each surface of the test workpieces was machined by face milling at a 1.5-mm thickness. In these experiments, six slots were made along the workpiece block on each surface under different cooling conditions. **Table 3** and **Table 4** list the level parameters and experimental parameters used, respectively.

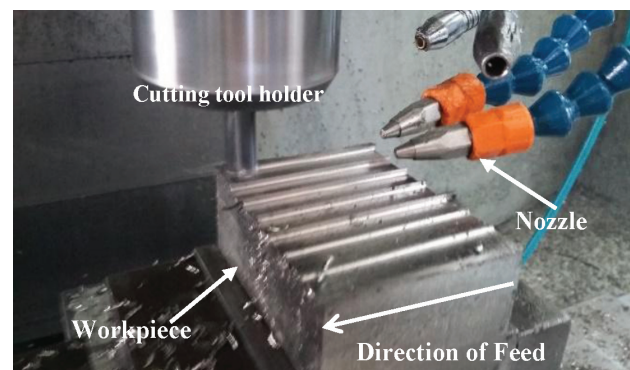
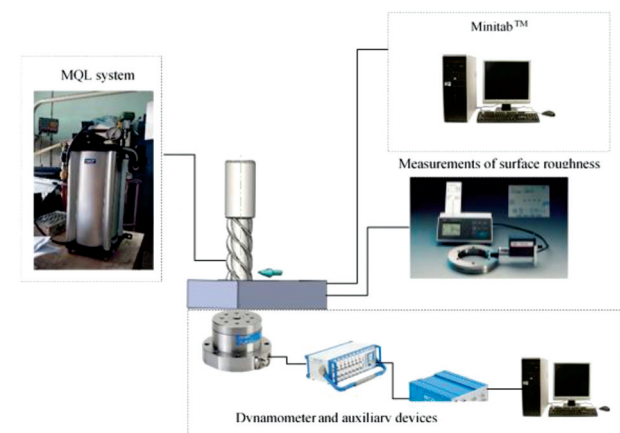
To measure the machining forces during slot milling, blocks of the titanium alloy Ti-6Al-4V workpiece were

Table 2: Literature survey using RSM with MQL technique when machining titanium alloy

ref.	material	machining process	RSM	control parameters	response
28	stainless steel 304	turning	CCD ¹⁾	v_c	R_a
				f	
				a_p	
29	Cu alloy C360	milling	CCD	v_c	R_a , machining time
				f	
				a_p	
30	Ti alloy Ti-6Al-4V	milling	CCD	v_c	R_a
				f	
				a_p	
31	Ti alloy Ti-6Al-4V	turning	CCD	v_c	R_a , F_c
				f	
				a_p	
32	Ti Grade 2	turning	BB ²⁾	v_c	R_a
				f	
				Type of nanofluids	
33	Ti alloy Ti-6Al-4V	milling	CCD	v_c	power consumption, material removal rate, R_a , tool wear
				f	
				a_p	
34	Ti Grade 2	turning	BB	v_c	F_c , R_a , tool wear
				f	
				approach angle	

1) CCD – Central Composite Design

2) BB – Box-Behkvens

**Figure 1:** Slot milling with MQL technique**Figure 2:** Experimental setup for output measurement and data analysis

mounted and fixed on a three-axis dynamometer (Kistler 9272-A) under the blocks. The setup was arranged for a cutting-force measurement, including a charge amplifier, and was transferred to a PC through the DynoWare software to obtain the values of the real cutting force (F_x , F_y , F_z) and conduct a computational analysis of the signal trends in the slot milling experiments. The mean cutting force (F_c) can be calculated by Equation (1):

$$F_c = \sqrt{F_x^2 + F_y^2 + F_z^2} \quad (1)$$

Measurements of the surface roughness were performed with a Mahr M1 perthometer.

Table 3: Parameters and levels

factor	levels				
v_c /(m/min)	56.835	60	65	70	73.165
f /(mm/tooth)	0.010505	0.02	0.035	0.05	0.059495
a_p /mm	0.6835	1	1.5	2	2.3165
Q /(mL/h)	18.8855	23	29.5	36	40.1145
Coding	-1.633	-1	0	1	1.633

Table 4: Experimental parameters used

machining type	Slot Milling
materials	Ti-6Al-4V
cutting tool	coated cementite carbide (coated Al Cr x Ni)
machining parameters	feed rate: (0.02; 0.03; 0.04; 0.05) mm/tooth cutting speed: (50; 60; 70) m/min radial depth of cut: 10 mm axial depth of cut: (1; 2; 3) mm
cooling technique	flood, dry and MQL
MQL	cutting-fluid type: fatty acid ester cutting-fluid flow rate: (18; 29.5; 36; 40) mL/h compressed-air pressure: 3 bar

3 RESULTS AND DISCUSSION

3.1 Residual analysis of responses under MQL condition

Residual plots are important tools for evaluating the adequacy of regression models.^{16–36} In general, there are four types of plot: normal probability plot, residual-vs.-fitted plot, residual histogram plot, and residual-vs.-observation-order plot.

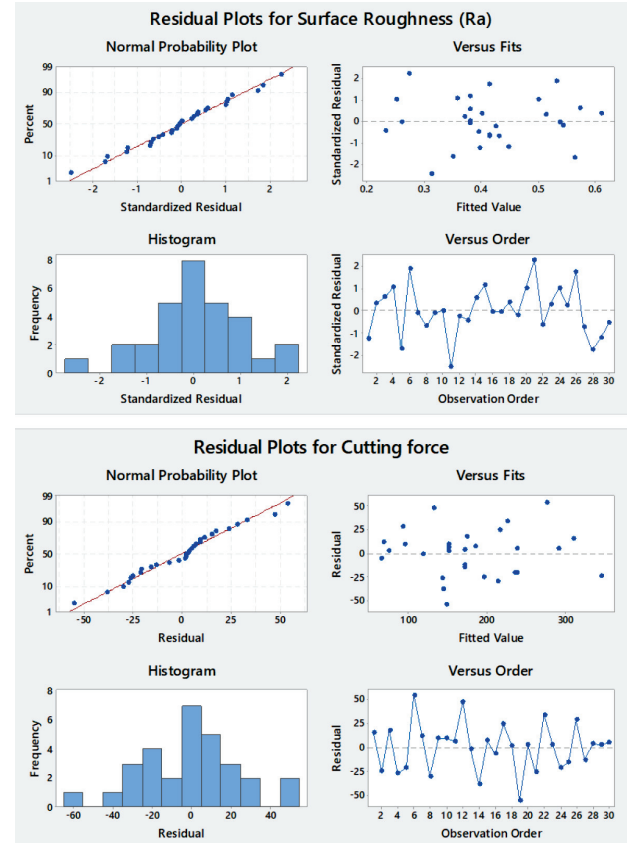


Figure 3: Residual analysis of MQL conditions

Table 5: Analysis of variance (ANOVA) considering F_c values

Source	flood			dry			MQL		
	F-Value	P-Value	Contribution	F-Value	P-Value	Contribution	F-Value	P-Value	Contribution
Model	28.80	0.000	96.97 %	8.87	0.002	90.79 %	7.88	0.000	89.41 %
linear	86.34	0.000	87.20 %	20.32	0.000	62.38 %	25.32	0.000	76.62 %
v_c /(m/min)	0.10	0.757	0.03 %	1.52	0.248	1.56 %	1.55	0.234	1.17 %
f /(mm/tooth)	70.03	0.000	23.58 %	26.87	0.001	27.50 %	43.45	0.000	32.88 %
a_p /mm	188.89	0.000	63.59 %	32.55	0.000	33.32 %	23.17	0.000	17.53 %
Q /(mL/h)	—	—	—	—	—	—	33.10	0.000	25.04 %
S	15.355			37.345			35.212		
R-squared	96.97 %			90.79 %			89.41 %		
Adj R-squared	93.60 %			80.56 %			78.00 %		

Regression models for F_c :

$$F_{c \text{ DRY}} = 5745 - 180.7 \cdot v_c + 14737 \cdot f - 281 \cdot a_p + 1.488 \cdot v_c^2 + 81668 \cdot f^2 + 133.4 \cdot a_p^2 - 276 \cdot v_c \cdot f - 0.41 \cdot v_c \cdot a_p + 671 \cdot f \cdot a_p$$

$$F_{c \text{ FLOOD}} = -992 + 26.2 \cdot v_c + 2262 \cdot f + 180 \cdot a_p - 0.173 \cdot v_c^2 - 51692 \cdot f^2 + 13.2 \cdot a_p^2 + 5.6 \cdot v_c \cdot f - 2.79 \cdot v_c \cdot a_p + 2225 \cdot f \cdot a_p$$

$$F_{c \text{ MQL}} = 2574 - 74.5 \cdot v_c - 3241 \cdot f - 128 \cdot a_p + 5.7 \cdot Q + 0.602 \cdot v_c^2 - 24353 \cdot f^2 + 91.3 \cdot a_p^2 - 0.066 \cdot Q^2 + 154 \cdot v_c \cdot f - 2.77 \cdot v_c \cdot a_p - 0.105 \cdot v_c \cdot Q + 1468 \cdot f \cdot a_p - 133.4 \cdot f \cdot Q + 1.92 \cdot a_p \cdot Q$$

The residual plot for all responses under various cooling/lubrication conditions is shown in **Figure 3**. According to the normal probability plot, the points of the data are in good arrangement on a straight line; therefore, the normality assumptions are valid. The residuals-vs.-experiment data are spread up and down the zero line. Upon examination of all the residual and probability graphs, it was concluded that the models are capable of accurately estimating R_a and F_c for different cooling conditions. The residual-vs.-fitted plots for R_a and F_c revealed that the data points are randomly scattered; as a result, the assumption of constant variance is correct.

3.2 Cutting force (F_c)

A statistical analysis of the data was carried out in the form of a variance analysis using MINITAB™ 17 software. Per the ANOVA results, it is noticeable from **Table 5**, depending on the p-value, that the feed per tooth, depth of cut and cutting fluid flow rate are statistically significant ($p < 0.005$). In addition, the F-value statistics report the same result and contribution value. The feed per tooth and depth of cut were the most effective factors

in the cutting force under flood and dry conditions. However, under MQL conditions, the feed per tooth and cutting fluid flow rate were the most effective factors.

The cutting-zone temperature (tool-chip interface) rises to the softening temperature of the titanium alloy, increasing the material removal rate and decreasing the thickness of the chip. Similar effects during the milling of titanium alloy were found in other studies.^{31–36} In **Figure 4**, a general trend can be noticed: the F_c increased with an increasing feed per tooth and depth of cutting. In addition, at low machining conditions, F_c was reduced under both MQL and flood conditions. However, F_c increased again when the feed per tooth increased from 0.02 mm/tooth to 0.05 mm/tooth and the cutting depth rose from 1 mm to 2 mm. With the feed per tooth increasing from 0.02 to 0.05 mm/tooth, the material-removed rate also increased. Under such conditions, the cutting tool has to undergo a considerable cutting load, thus generating a high cutting temperature and possibly affecting the physical properties of the cutting tool.^{20–37} The outcome is an increased mean F_c for all levels of feed per tooth. More specifically, the maximum values of F_c under dry, flood, and MQL conditions were about (403.25; 287.82; 330.08) N, respectively, and the minimum values of F_c were about (99.71; 54.30; 58.39) N, respectively.

Figure 5 depicts the F_c under different machining conditions. Accordingly, dry conditions produced the highest F_c for all machining conditions. However, the F_c values were equally acceptable under the MQL condition when compared with the flood condition. At higher machining conditions of $v_c = 70$ m/min, $f = 0.05$ mm/tooth, and $a_p = 2$ mm, the lowest F_c was observed with MQL at 216.77 N. The results showed that milling titanium under MQL led to improved F_c values, while the worst values were yielded under dry conditions.

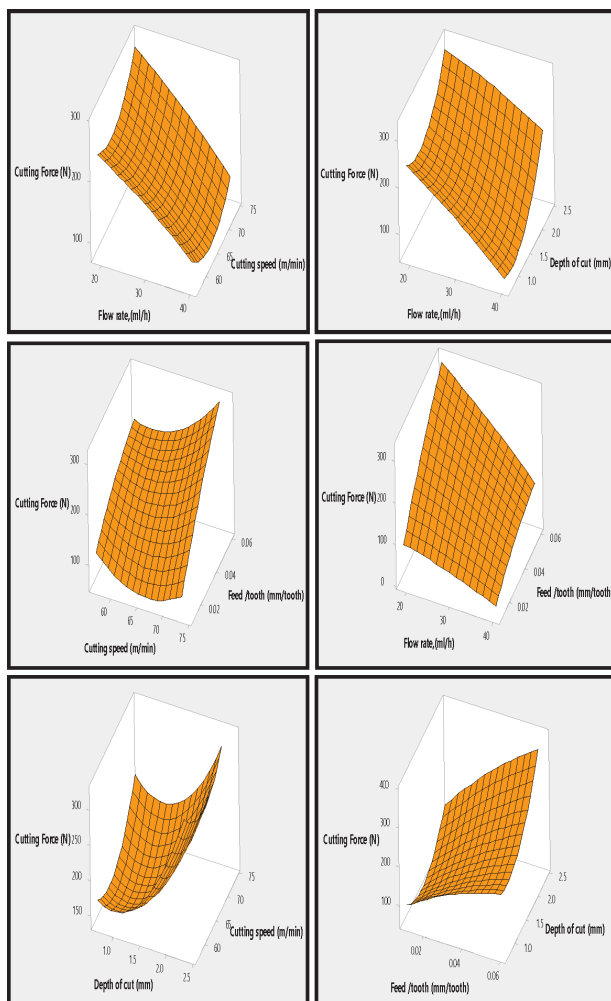


Figure 4: Cutting-force results for MQL condition

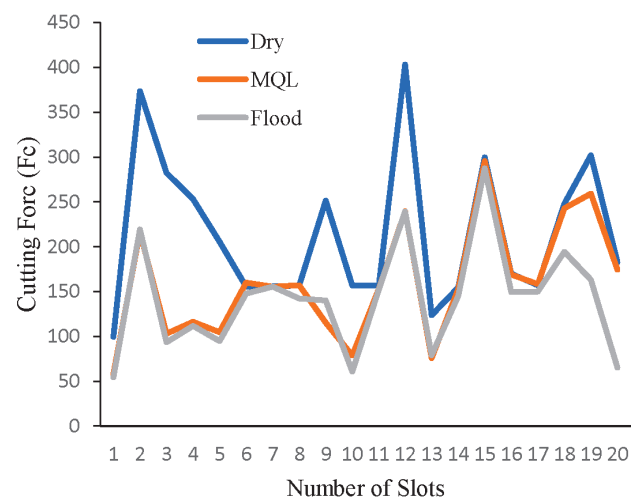


Figure 5: Cutting-force results for different cooling/lubrication conditions

3.3 Surface roughness (R_a)

Per the ANOVA results, it is noticeable from **Table 6**, depending on the p-value, that the feed per tooth, depth

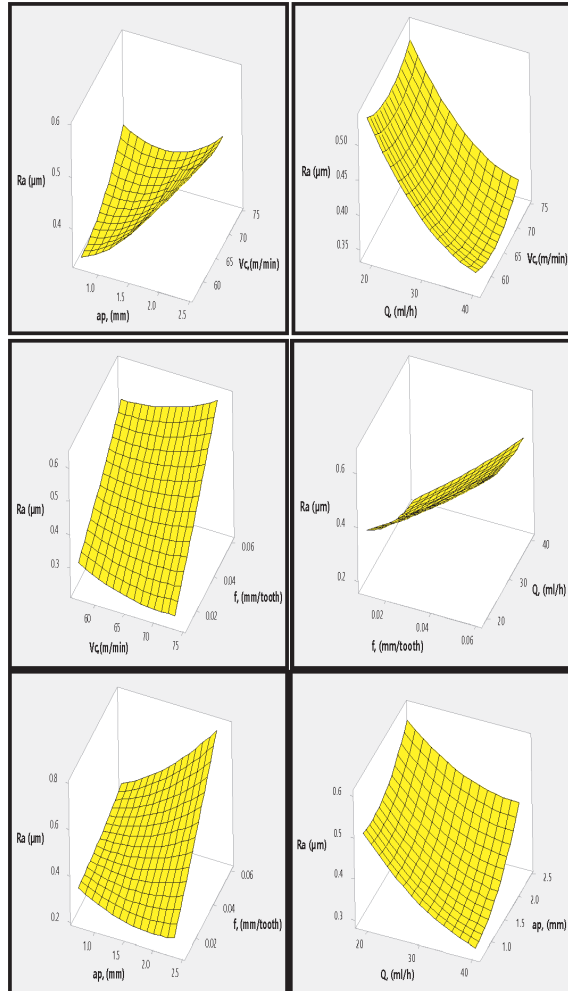


Figure 6: Effects of machining parameters on surface roughness (MQL condition)

of cut and cutting-fluid flow rate are statistically significant ($p < 0.005$). In addition, the F-value statistics report the same results. In the meantime, the values of feed per tooth were the most effective factors in the surface roughness under all conditions. Similar results were reported in.³⁸

The R_a values vs. machining parameters are shown in **Figure 6** under the MQL condition. It is clear that R_a grew quite quickly with increased feed rates from 0.02 mm/tooth to 0.05 mm/tooth and decreased as the cutting fluid flow (FCs) rate increased. The results for the R_a values were plotted against the flow rates for a 60–70 m/min cutting speed and feed levels of (0.02; 0.05) mm/tooth, as shown in **Figure 7**.

The R_a results were compared in terms of average, maximum, and minimum values for a cutting speed of 70 m/min and feed levels of (0.02; 0.05) mm/tooth. It was observed that machining under MQL and flood conditions yielded better R_a values than the dry conditions. Similar results were shown in other studies.^{39,40} The R_a values for MQL of $Q = 23$ mL/h and $Q = 36$ mL/h were found to be different from each other. Meanwhile, the values of R_a under MQL at $Q = 23$ mL/h and the dry condition were very close to each other, but there was an improvement with an increased flow rate to $Q = 36$ mL/h.

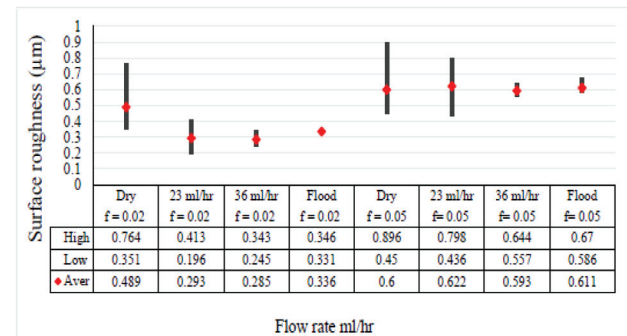


Figure 7: Surface roughness results at feed rates of 0.02–0.05 mm/tooth and cutting speed of 70 m/min

Table 6: Analysis of variance (ANOVA) considering R_a values

	flood	dry	MQL						
Source	F-Value	P-Value	contribution	F-Value	P-Value	contribution	F-Value	P-Value	contribution
model	13.89	0.000	92.59 %	6.13	0.005	84.65 %	5.45	0.001	85.37 %
linear	32.28	0.000	71.74 %	13.63	0.001	62.99 %	16.00	0.000	66.86 %
v_c /(m/min)	1.34	0.274	0.99 %	2.5	0.145	3.84 %	0.00	0.964	0.04 %
f /(mm/tooth)	77.71	0.000	57.57 %	30.13	0.000	46.26 %	49.59	0.000	51.82 %
a_p /mm	17.79	0.002	13.18 %	8.39	0.016	12.89 %	7.50	0.016	7.84 %
Q /(mL/h)	—	—	—	—	—	—	6.89	0.020	7.20 %
S	0.039			0.0539			0.0644		
R-squared	92.59 %			84.65 %			85.37 %		
Adj R-squared	85.92 %			70.83 %			69.70 %		

Regression models for R_a :

$$R_{a \text{ DRY}} = -4.59 + 0.1529 \cdot v_c + 15.2 \cdot f - 0.548 \cdot a_p - 0.001089 \cdot v_c^2 + 77.3 \cdot f^2 + 0.1611 \cdot a_p^2 - 0.262 \cdot v_c \cdot f + 0.00165 \cdot v_c \cdot a_p + 1.22 \cdot f \cdot a_p$$

$$R_{a \text{ FLOOD}} = -7.15 + 0.2360 \cdot v_c + 10.9 \cdot f - 0.559 \cdot a_p - 0.001877 \cdot v_c^2 - 126 \cdot f^2 + 0.0673 \cdot a_p^2 + 0.037 \cdot v_c \cdot f + 0.006 \cdot v_c \cdot a_p + 1.23 \cdot f \cdot a_p$$

$$R_{a \text{ MQL}} = 0.92 - 0.0177 \cdot v_c - 14.1 \cdot f - 0.009 \cdot a_p - 0.014 \cdot Q + 0.000325 \cdot v_c^2 + 16.2 \cdot f^2 + 0.058 \cdot a_p^2 + 0.00029 \cdot Q^2 + 0.225 \cdot v_c \cdot f - 0.00820 \cdot v_c \cdot a_p - 0.00677 \cdot v_c \cdot Q + 5.93 \cdot f \cdot a_p - 0.136 \cdot f \cdot Q + 0.00804 \cdot a_p \cdot Q$$

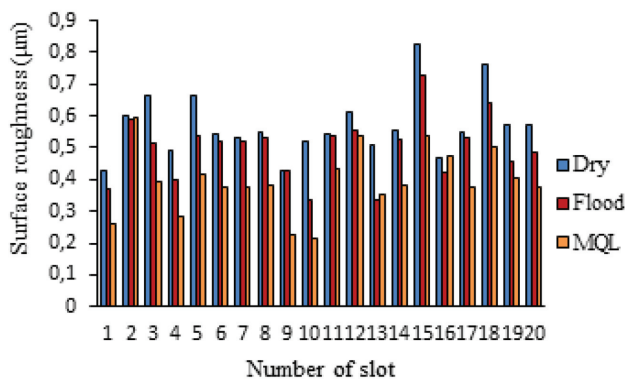


Figure 8: Surface-roughness results under different cooling/lubrication conditions

Figure 8 shows the R_a values under different machining conditions. It can be noted that MQL outperformed the dry and flood conditions under all machining conditions and that the dry condition provided the highest R_a values. This can be explained as follows: the diameter of the droplets is reduced along with an increased fluid flow rate, which can better penetrate the contact zones. Thus, the lubrication improves, as the friction is reduced.⁴¹ However, the latter yielded more satisfactory outcomes at a cutting speed of 60 m/min and feed level of 0.02 mm/tooth.

The better results of MQL (36 mL/h) proved to be an optimum value of the flow rate for this condition. It was important to observe, with respect to the R_a result, that the increase in the cutting-fluid flow rate with MQL of more than 36 mL/h did not provide any improvement. Therefore, there is a concern as to the optimal level of the flow rate. In this respect, a possible contributor may be the lubrication capacity and the associated penetration of the cutting fluid with the MQL technique.²⁰

5 CONCLUSIONS

In this study, a titanium alloy was slot milled using different cooling/lubrication conditions (dry, MQL and flood) to investigate the effect of the MQL condition on the cutting force and surface roughness. The main conclusions can be drawn as follows:

The regression model functions were validated by ANOVA analysis with high coefficients of determination (R^2) and at a level of $p < 0.05$ for the three cooling/lubrication conditions. The ANOVA results have indicated that the cutting force and surface roughness are largely affected by the feed rate, depth of cut and cutting-fluid flow rate.

The response surface methodology (RSM) exhibited an acceptable degree of ability to reduce the complexity of the problem by identifying the unimportant factors in the model.

The MQL proved to be an effective technique to achieve sustainability requirements and is an effective al-

ternative approach for conventional cooling conditions during the machining of a titanium alloy (Ti-6Al-4V) in terms of improving the surface roughness and cutting force by eliminating the problems of flood cooling. It was found that the MQL condition generates lower values of surface roughness with values of 0.425 μm , 0.329 μm , and 0.227 μm for dry, flood, and MQL conditions, respectively. Meanwhile, the cutting-force values under the MQL condition were found to be close to those of the flood condition and at times even better.

The flow rates of the cutting fluid increased to 36 mL/h when milling under the MQL technique. This led to a minimization of the cutting force and surface roughness when compared to all the cooling/lubrication conditions. This is, in particular, the case with a low feed rate and low cutting speed. The effects of the flow rate of the cutting fluid seem to be more dominant. A better machining performance was found at a flow rate of 36 mL/h under machining conditions $f = 0.02$ mm/tooth and $v_c = 60$ m/min.

Future work may study the improved performance of the milling process under the MQL technique through improved cooling capacity and the lubrication effect of the cutting fluid using nanoparticles. In addition, it is necessary to optimize the MQL parameters for the sustainable machining of titanium alloys. This trend should be studied in detail by carrying out an experiment to identify the optimal combination of parameters for the machining process and MQL technique.

6 REFERENCES

- ¹ A. A. Munoz, P. Sheng, An analytical approach for determining the environmental impact of machining processes, *Journal of Materials Processing Technology*, 53 (1995) 3–4, 736–758, doi:10.1016/0924-0136(94)01764-R
- ² F. Klocke, K. Gerschwiler, R. Fritsch, D. Lung, PVD-coated tools and native ester: An advanced system for environmentally friendly machining, *Surface and Coatings Technology*, 201 (2006) 7, 4389–4394, doi:10.1016/j.surfcoat.2006.08.089
- ³ D. Sujan, M. M. Reddy, Q. S. Yi, Influence of cutting fluid conditions and cutting parameters on surface roughness and tool wear in turning process using Taguchi method, *Measurement*, 78 (2016), 111–119, doi:10.1016/j.measurement.2015.09.011
- ⁴ G. T. Smith, *Cutting tool technology: Industrial handbook*, Springer, London, 2008, doi:10.1007/978-1-84800-205-0
- ⁵ M. Rahman, A. S. Kumar, M. U. Salam, Experimental evaluation on the effect of minimal quantities of lubricant in milling, *International Journal of Machine Tools and Manufacture*, 42 (2002) 5, 539–547, doi:10.1016/S0890-6955(01)00160-2
- ⁶ M. Mozammel, Mathematical modeling and optimization of MQL assisted end milling characteristics based on RSM and Taguchi method, *Measurement*, 121 (2018), 249–260, doi:10.1016/j.measurement.2018.02.017
- ⁷ A. R. Motorcu, A. Kuş, I. Durgun, The evaluation of the effects of control factors on surface roughness in the drilling of Waspaloy superalloy, *Measurement*, 58 (2014), 394–408, doi:10.1016/j.measurement.2014.09.012
- ⁸ A. K. Sharma, A. K. Kiwari, A. R. Dixit, Effects of Minimum Quantity Lubrication (MQL) in machining processes using conventional and nano-fluid based cutting fluids: A comprehensive review, *Journal*

- of Cleaner Production, 127 (2016), 1–18, doi:10.1016/j.jclepro.2016.03.146
- ⁹ C. S. Ghosh, P. V. Rao, Application of sustainable techniques in metal cutting for enhanced machinability: A review, *Journal of Cleaner Production*, 100 (2015), 17–34, doi:10.1016/j.jclepro.2015.03.039
- ¹⁰ E. Brinksmeier, A. Walter, R. Janssen, P. Diersen, Aspects of cooling lubrication reduction in machining advanced materials, *Proceedings of the Institution of Mechanical Engineers, Part B: Journal of Engineering Manufact.*, 213 (1999) 8, 769–778, doi:10.1243/0954405991517209
- ¹¹ S. Zhang, J. F. Li, Y. W. Wang, Tool life and cutting forces in end milling Inconel 718 under dry and minimum quantity cooling lubrication cutting conditions, *Journal of Cleaner Production*, 32 (2012), 81–87, doi:10.1016/j.jclepro.2012.03.014
- ¹² Y. Kamata, T. Obikawa, High speed MQL finish-turning of Inconel 718 with different coated tools, *Journal of Materials Processing Technology*, 192–193 (2007), 281–286, doi:10.1016/j.jmatprotec.2007.04.052
- ¹³ L. R. Silva, E. C. Bianchi, R. E. Catai, R. Y. Fosse, T. V. Franca, P. R. Aguiar, Study on the behavior of the minimum quantity lubricant-MQL technique under different lubricating and cooling conditions when grinding ABNT 4340 steel, *Journal of the Brazilian Society of Mechanical Sciences and Engineering*, 27 (2005) 2, 192–199, doi:10.1590/S1678-58782005000200012
- ¹⁴ N. R. Dhar, M. Kamruzzaman, M. Ahmed, Effect of minimum quantity lubrication (MQL) on tool wear and surface roughness in turning AISI-4340 steel, *Journal of Materials Processing Technology*, 172 (2006) 2, 299–304, doi:10.1016/j.jmatprotec.2005.09.022
- ¹⁵ T. Obikawa, Y. Kamata, Y. Asano, K. Nakayama, A. W. Otieno, Micro-liter lubrication machining of Inconel 718, *International Journal of Machine Tools and Manufacture*, 48 (2008) 15, 1605–1612, doi:10.1016/j.ijmachtools.2008.07.011
- ¹⁶ A. C. Okafor, P. M. Jasra, Effects of cooling strategies and tool coatings on cutting forces and tooth frequency in high-speed down-milling of Inconel-718 using helical bull-nose solid carbide end mills, *The International Journal of Advanced Manufacturing Technology*, 97 (2008), 2301–2318, doi:10.1007/s00170-018-2096-5
- ¹⁷ W. Zhao, N. He, L. Li, High speed milling of Ti6Al4V alloy with minimal quantity lubrication, *Key Engineering Materials*, 329 (2007), 663–668, doi:10.4028/www.scientific.net/KEM.329.663
- ¹⁸ M. S. Ahmad Yasir, C. H. Che Hassan, A. G. Jaharah, H. E. Nagi, B. Yanuar, A. I. Gusri, Machinability of Ti-6Al-4V under dry and near dry condition using carbide tools, *The Open Industrial and Manufacturing Engineering Journal*, 2 (2009), 1–9, doi:10.2174/1874152500902010001
- ¹⁹ K. K. Joshi, K. R. Anurag, An experimental investigation in turning of Incoloy 800 in dry, MQL and flood cooling conditions, *Procedia Manufacturing*, 20 (2018), 350–357, doi:10.1016/j.promfg.2018.02.051
- ²⁰ A. H. Tazehkandi, M. Shabgard, F. Pilehvarian, On the feasibility of a reduction in cutting fluid consumption via spray of biodegradable vegetable oil with compressed air in machining Inconel 706, *Journal of Cleaner Production*, 104 (2015), 422–435, doi:10.1016/j.jclepro.2015.05.039
- ²¹ E. O. Ezugwu, Key improvements in the machining of difficult-to-cut aerospace superalloys, *International Journal of Machine Tools and Manufacture*, 45 (2005) 12–13, 1353–1367, doi:10.1016/j.ijmachtools.2005.02.003
- ²² H. A. Kishawy, M. Dumitrescu, E. G. Ng, M. A. Elbestawi, Effect of coolant strategy on tool performance, chip morphology and surface quality during high-speed machining of A356 aluminium alloy, *International Journal of Machine Tools and Manufacture*, 45 (2005) 2, 219–227, doi:10.1016/j.ijmachtools.2004.07.003
- ²³ J. Sun, Y. S. Wong, M. Rahman, Z. G. Wang, K. S. Neo, C. H. Tan, H. Onozuka, Effects of coolant supply methods and cutting conditions on tool life in end milling titanium alloy, *Machining Science and Technology*, 10 (2006), 355–370, doi:10.1080/10910340600902181
- ²⁴ E. A. Rahim, H. Sasahara, Investigation of tool wear and surface integrity on MQL machining of Ti-6Al-4V using biodegradable oil, *Proceedings of the Institution of Mechanical Engineers, Part B: Journal of Engineering Manufacture*, 225 (2011) 9, 1505–1511, doi:10.1177/0954405411402554
- ²⁵ P. J. Arrazola, T. Ozel, D. Umbrello, M. Davies, I. S. Jawahir, Recent advances in modelling of metal machining processes, *CIRP Annals-Manufacturing Technology*, 62 (2013) 2, 695–718, doi:10.1016/j.cirp.2013.05.006
- ²⁶ A. D. Jayal, F. Badurdeen, O. W. Dillon, I. S. Jawahir, Sustainable manufacturing: Modelling and optimization challenges at the product, process and system levels, *CIRP Journal of Manufacturing Science and Technology*, 2 (2010) 3, 144–152, doi:10.1016/j.cirpj.2010.03.006
- ²⁷ T. Ozel, Y. Karpat, Predictive modelling of surface roughness and tool wear in hard turning using regression and neural networks, *International Journal of Machine Tools and Manufacture*, 45 (2005) 4–5, 467–479, doi:10.1016/j.ijmachtools.2004.09.007
- ²⁸ I. Asiltürk, S. Neşeli, Multi response optimisation of CNC turning parameters via Taguchi method-based response surface analysis, *Measurement*, 45 (2012) 4, 785–794, doi:10.1016/j.measurement.2011.12.004
- ²⁹ S. P. Leo Kumar, Experimental investigations and empirical modelling for optimization of surface roughness and machining time parameters in micro end milling using Genetic Algorithm, *Measurement*, 124 (2018), 386–394, doi:10.1016/j.measurement.2018.04.056
- ³⁰ K. H. Hashmi, G. Zakria, M. B. Raza, S. Khalil, Optimization of process parameters for high speed machining of Ti-6Al-4V using response surface methodology, *The International Journal of Advanced Manufacturing Technology*, 85 (2016), 1847–1856, doi:10.1007/s00170-015-8057-3
- ³¹ N. K. Sahu, A. B. Andhare, Multi-objective optimization for improving machinability of Ti-6Al-4V using RSM and advanced algorithms, *Journal of Computational Design and Engineering*, 6 (2018) 1, 1–12, doi:10.1016/j.jcde.2018.04.004
- ³² M. K. Gupta, P. K. Sood, Surface roughness measurements in NFMQL assisted turning of titanium alloys: An optimization approach, *Friction*, 5 (2017), 155–170, doi:10.1007/s40544-017-0141-2
- ³³ N. K. Sahu, A. B. Andhare, Modelling and multiobjective optimization for productivity improvement in high speed milling of Ti-6Al-4V using RSM and GA, *Journal of the Brazilian Society of Mechanical Sciences and Engineering*, 39 (2017), 5069–5085, doi:10.1007/s40430-017-0804-y
- ³⁴ M. K. Gupta, P. K. Sood, G. Singh, V. S. Sharma, Sustainable machining of aerospace material Ti (grade-2) alloy: Modelling and optimization, *Journal of Cleaner Production*, 147 (2017), 614–627, doi:10.1016/j.jclepro.2017.01.133
- ³⁵ G. Rotella, O. W. Dillon, D. Umbrello, L. Settineri, I. S. Jawahir, The effects of cooling conditions on surface integrity in machining of Ti6Al4V alloy, *The International Journal of Advanced Manufacturing Technology*, 71 (2014), 47–55, doi:10.1007/s00170-013-5477-9
- ³⁶ M. Nouioua, M. A. Yallese, R. Khettabi, S. Belhadi, M. L. Bouhalais, F. Girardin, Investigation of the performance of the MQL, dry, and wet turning by response surface methodology (RSM) and artificial neural network (ANN), *The International Journal of Advanced Manufacturing Technology*, 93 (2017), 2485–2504, doi:10.1007/s00170-017-0589-2
- ³⁷ M. Sarikaya, A. Güllü, Multi-response optimization of minimum quantity lubrication parameters using Taguchi-based grey relational analysis in turning of difficult-to-cut alloy Haynes 25, *Journal of Cleaner Production*, 91 (2015), 347–357, doi:10.1016/j.jclepro.2014.12.020
- ³⁸ M. Z. A. Yazid, C. H. Che Haron, J. A. Ghani, G. A. Ibrahim, A. Y. M. Said, Surface integrity of Inconel 718 when finish turning with

- PVD coated carbide tool under MQL, *Procedia Engineering*, 19 (2011), 396–401, doi:10.1016/j.proeng.2011.11.131
- ³⁸ R. S. Revuru, J. Z. Zhang, N. R. Posinasetti, T. Kidd, Optimization of titanium alloys turning operation in varied cutting fluid conditions with multiple machining performance characteristics, *The International Journal of Advanced Manufacturing Technology*, 95 (2018), 1451–1463, doi:10.1007/s00170-017-1299-5
- ³⁹ M. J. Bermingham, J. Kirsch, S. Sun, S. Palanisamy, M. S. Dargusch, New observations on tool life, cutting forces and chip morphology in cryogenic machining Ti-6Al-4V, *International Journal of Machine Tools and Manufacture*, 51 (2011) 6, 500–511, doi:10.1016/j.jmachtools.2011.02.009
- ⁴⁰ L. Zhiqiang, Green machining of Ti-6Al-4V under Minimum Quantity Lubrication (MQL) condition, *Machining of Titanium Alloys Part of the Materials Forming, Machining and Tribology*, Springer, Berlin, 2014, 113–129, doi:10.1007/978-3-662-43902-9_5
- ⁴¹ N. Fang, Q. Wu, A comparative study of the cutting forces in high speed machining of Ti-6Al-4V and Inconel 718 with a round cutting edge tool, *Journal of Materials Processing Technology*, 209 (2009) 9, 4385–4389, doi:10.1016/j.jmatprotec.2008.10.013